

개선된 Iron-molybdate 촉매를 이용한 메탄올에서 포름알데히드의 산화 탈수소화반응 연구

김태환*, 추고연, 최정식¹, B.Ramachandra², M.B.Saidutta³

한국에너지기술연구원, 충남대학교 화학공학과¹, National Institute of Technology Karnataka
화학공학과², National Institute of Technology Karnataka 화학공학과³
(thkim@kier.re.kr*)

Modified Iron-Molybdate catalysts for oxidative dehydrogenation of methanol to formaldehyde

Tae-Hwan Kim*, Ko-Yeon Choo, Jung-Sik Choi¹, B.Ramachandra², M.B.Saidutta³

Korea Institute of Energy Research (KIER),
Department of Chemical Engineering, Chungnam National University¹,
Department of Chemistry, National Institute of Technology Karnataka, Surathkal-575025, India²
Department of Chemical Engineering, National Institute of Technology Karnataka, Surathkal-575025,
India³
(thkim@kier.re.kr*)

1. Introduction

Formaldehyde is one of the important basic chemicals and is required for the manufacture of a number of industrial and consumer products. The commercial synthesis of formaldehyde is by dehydrogenation and oxidation of methanol on metallic silver, operating at high temperature and in deficiency of air, or oxidation of methanol in considerable excess of air on metal oxide catalysts, operating at relatively low temperatures (220°-450°C). The processes, which use metal oxide as catalysts, have with respect to those using metallic silver, the advantages of higher yields in formaldehyde and complete methanol conversion. In consequence, one does not need to recover the unaltered methanol from the reaction products and aqueous solutions of formaldehyde, which are substantially free from alcohol, are obtained. The growing industrial importance of Mo-Fe oxide catalysts has led to good number of investigations.

In the present investigation the activity of the modified Mo/Fe catalyst was studied for the conversion of methanol and selectivity towards formaldehyde for various residence times.

2. Experimental

2.1. Preparation of catalysts

The catalyst was prepared based on the procedure given in [1]. The Mo/Fe catalyst with atomic ratios of 1.5 and 3.0 were prepared by co-precipitation from an aqueous solution of Fe(NO₃)₃·9H₂O and (NH₄)₆Mo₇O₂₄. Iron nitrate solution was slowly added to the cold solution of ammonium hepta molybdate acidified with nitric acid under vigorous stirring. After total addition of iron solution, the precipitates were ripened in contact with mother liquors at 98°C for 3 h under stirring. During this period, the Mo/Fe=1.5 yellowish precipitate changes to pale green color and dark yellow colored Mo/Fe=3 was obtained.

After ripening, the precipitates were filtered, dried at 118°C overnight, and calcined at 373°C for 10 h in airflow.

2.2. Characterization of catalysts

The BET surface area, pore size distribution and pore volume were measured with a Micrometrics ASAP-2010 apparatus. The morphology, chemical analysis and homogeneity of the prepared catalysts were examined by FE-SEM (LEO-1530FE). The XRD for the catalysts were obtained on Rigaku (D/Max2000-Ultima plus; X-ray radiation, CuK α).

2.3. Catalytic tests

The oxidation of the methanol was carried out in a fixed bed reactor at atmospheric pressure. The activity of the catalyst was examined by taking fixed quantity of the catalyst and variable reaction conditions. The feed mixtures were prepared by injecting liquid methanol in to nitrogen flow with a precise 301 HPLC pump. To prevent the polymerization of the formaldehyde, out lets were kept at 120°C. Analyses of the reaction products were done using online Shimadzu GC-2010 gas chromatograph with a thermal conductivity detector.

3. Results and discussion

3.1. Characterization of catalysts

The BET surface area for the modified Mo/Fe=1.5 is 2.0 m²/g and for the Mo/Fe=3.0 it is 3.2 m²/g. This is in agreement with [1, 2]. This shows that the surface area of the prepared catalyst increases with Mo content in the bulk. The Mo/Fe=3.0 has lower surface area than the conventional catalyst of the same ratio, which can be attributed to a less content of the Mo in the bulk due to the treatment with nitric acid.

The scanning electron micrographs (Fig. 1,2) for the prepared catalyst show an ordered *lamellae* morphology. The morphological appearance is in accordance with surface area of the catalyst [3]. It can be seen from the figure that no fiber-like material, usually assignable to the MoO₃ phase [4], was found in the prepared catalysts, which is a good indication that no phase segregation occurred during the precipitation and calcination steps. The segregation of MoO₃ is a frequent and adverse occurrence during the preparation of iron molybdenum mixed oxides. In fact, such an occurrence must be prevented because the MoO₃ phase is much less active for the selective oxidation of methanol than iron molybdate. Moreover, segregation of MoO₃ can lead to a Fe-rich phase that promotes total oxidation of methanol [5].

3.2. Catalytic behavior

The results of conversion of methanol and selectivity towards formaldehyde for various residence times were studied. The yield of formaldehyde for various residence times is also examined. Fig. 3 shows the conversion of methanol for various residence times, viz. 22.21, 44.42 and 83.91 g_{cat}·h/mol_{MeOH}. It can be seen that as the residence time increases the conversion of methanol also increases, indicating normal kinetics. The selectivity of formaldehyde formation for various residence times is presented in Fig. 4. It can be seen that as the residence time increases the selectivity of formaldehyde decreases. This is due to the subsequent oxidation of formaldehyde to carbon monoxide, due to longer residence times. From Fig. 5, the yield of formaldehyde for various residence times gives the idea that as the residence time increases the yield of formaldehyde decreases. This is due to the subsequent oxidation of formaldehyde to carbon monoxide, due to longer residence times.

4. Conclusion

The present work demonstrates that the modified Mo/Fe=3.0 catalyst show a ordered lamellae and the results of the catalytic tests evidence that the activity is not affected by modification, suggesting that the Fe₂(MoO₄)₃ phase would be the active phase of the catalyst. However the increase in residence time decreases the selectivity of formaldehyde. This is due to the subsequent oxidation of formaldehyde to carbon monoxide, due to longer residence times.

Acknowledgements

We gratefully acknowledge financial support from the Carbon Dioxide Reduction & Sequestration Center, one of 21st Century Frontier R&D Programs funded by the Ministry of Science and Technology of Korea.

Reference

1. A.P.V. Soares, M.Farinha Portela, A. Kiennemann, L. Hilaire and J.M.M. Millet, *App. Catal.A:General* **206** (2001)221-229.
2. P.Courty, Process for manufacturing iron molybdate catalyst of high strength and the use of the resulting catalyst in the catalytic oxidation of alcohols to aldehydes, *US Patent* 3,846,341 (1974).
3. M.R. Sun-Kou, S. Mendioroz, J.L.G. Fierro, J.M. Palacios, A. guerrero-Ruiz, *J.Mater.Sci.* **30** (1995) 496.
4. J.Arruano, S. Wanke, *Can.J.Chem.Engg.* **53** (1975)306.
5. G.D. Kolovertnov, G.K. Borekov, V.A. Dzisko, B.I. Popov, D.V. Tarasova, G.C. Belugina, *Kinet.Catal. (Engl. Transl.)* **6(6)** (1965) 950.

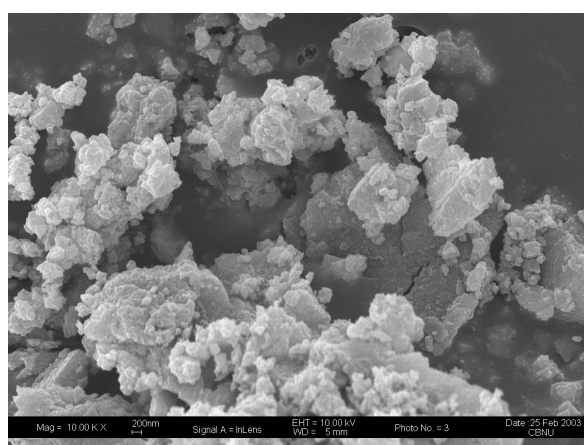
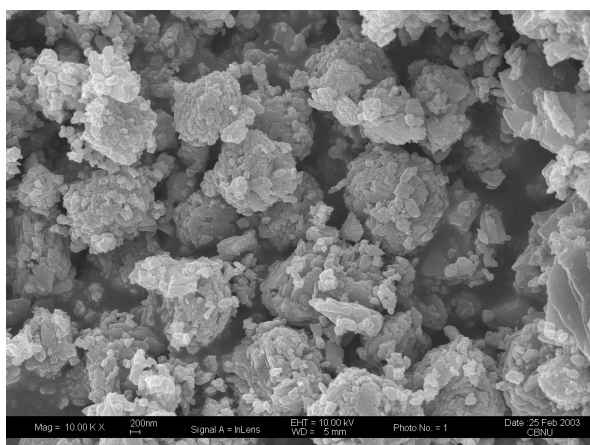


Fig. 1. SEM image of Mo/Fe=1.5 catalyst.

Fig. 2. SEM image of Mo/Fe=3.0 catalyst.

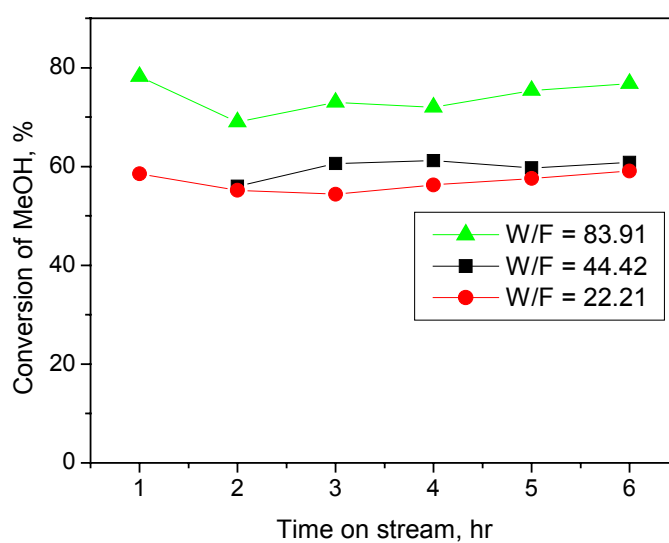


Fig. 3. Conversion of MeOH with three different W/F conditions.

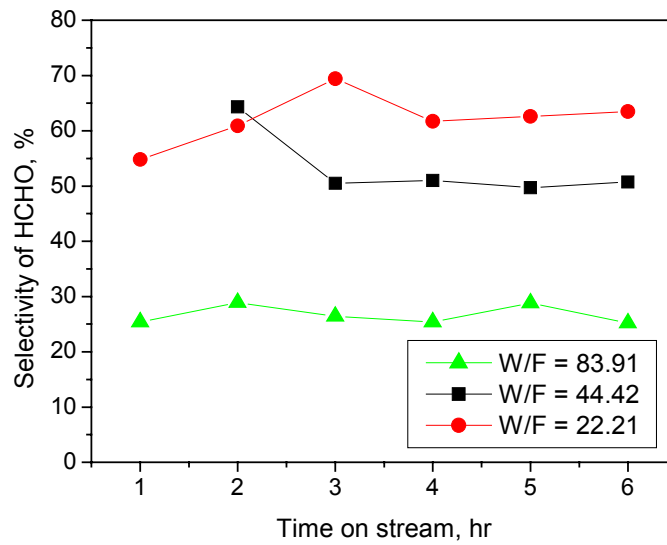


Fig. 4. Selectivity of HCHO with three different W/F conditions.

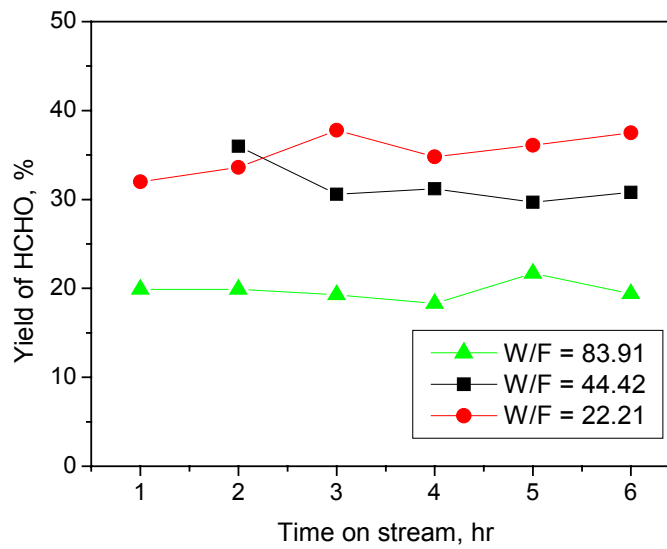


Fig. 5. Yield of HCHO with three different W/F conditions.